Research Article

Journal of
Environmental
Nanotechnology

Synthesis, Kinetics and Mathematical Modelling of Environment Friendly Acrylate-Based Binder

Sweta Shukla*, Prachi Jain and Soniya Juneja
Department of Applied Sciences, KIET Group of Institutions, Delhi/NCR, Ghaziabad, UP, India
Received: 04.05.2024 Accepted: 19.06.2024 Published: 30.06.2024
*sweta_hbti@rediffmail.com

ABSTRACT

The copolymers consisting of acrylic and methacrylic esters have achieved prime importance due to their versatile applications. Copolymerization of Methyl meth acrylate with butyl acrylate has been carried out for modifying the properties of the polymer. Dynamic swelling kinetics were conducted at room temperatures to investigate swelling properties of the synthesized binder for paint industries. The experimental swelling curves were analyzed using three different models- Peleg's model, the first-order absorption kinetic model, and the exponential association equation model. All of these models demonstrated excellent agreement with the experimental data, as indicated by high R^2 values and low values for Chi Square, Sum of Squared Errors, and Root Mean Square Error (RMSE). Comparing the determination coefficients for these models, it was concluded that the Peleg model provides a better representation of the swelling characteristics across various concentrations of the crosslinker in the polymer. Specifically, the Peleg model exhibited high R^2 values of 0.98121, 0.9869, and 0.97605 for 0%, 5%, and 10% polypropylene glycol diacrylate concentrations, respectively. Furthermore, it yielded reduced chi-square values of 1.44546, 0.74895, and 0.86587 and RMSE values of 1.202, 0.8654, and 0.9305 for the same respective concentrations. These results establish Peleg model as the most favorable choice for characterizing the swelling behavior with different cross linker concentrations in the polymer. The prepared latexes are used as binder for environment friendly coatings.

Keywords: Acrylate; Swelling; Kinetics; Polymer; Peleg model; First order absorption model; Exponential association model.

1. INTRODUCTION

In recent years, due to increased concerns about environmental protection, the emulsion polymerization technique has been selected as a green approach for the synthesis of polymers (Kane *et al.* 2008; Pladis *et al.* 2014; Kang *et al.* 2015). During the last few decades, polymer industry has been the fastest growing sector of chemical industry. Polymers are quite often used in agriculture, medicine, automobile parts, packing materials, adhesives, surface coatings, matrix for composites and elastomers. Surface coating is an important application of polymers for protecting a wide variety of substrates against mechanical, chemical, and atmospheric influences, while simultaneously enhancing their decorative appearance. A number of homopolymers and co-polymers are used as film-forming materials. The prime requirement for a polymer to form a film is its capacity to form bonds with different surfaces. For the last four decades solvent evaporation technique has been used for the preparation of films on various substrates. Due to environmental hazards related to solvent evaporation mechanism and its higher cost, the water borne cured films are emerging as better option for achieving superior properties in coating applications. The day to day increase in solvent costs is a major factor driving the development of water borne coatings. Among all polymeric binders, the acrylate-based binder is major in use for coating-based applications. Acrylic resins may be used alone or as a blend with other resins to form suitable binder system for coatings. Free radical polymerization of the acrylic resin has been reported earlier (McKenna *et al.* 1995). The relative ease of polymerization and wide range of properties among the acrylic resins have led to the commercial production of many different resins suitable for broad variety of applications (Zhu *et al.* 1990). For example, these resins play a prominent role in the paint industry due to the unique combination of their properties (Zhou *et al.* 2018). In this study, polyacrylate latex was synthesized by emulsion polymerization technique. The swelling characteristics like swelling ratio, swelling rate, diffusion kinetics, and activation energy of polymer latex were investigated based on the swelling values obtained at different time intervals. Only a few studies and models on the swelling kinetics of acrylate latex have been reported in the literature. The unique approach of this study entails the application of mathematical modelling, leveraging the Peleg model, exponential association equation model, and first-order absorption kinetic model to elucidate the swelling kinetics of acrylate latex, thus bridging existing gaps. Through a combination of empirical data and mathematical frameworks, our study offers fresh insights into this crucial facet of polymer behavior.

2. MATERIALS AND METHOD

2.1 Experimental Materials

Monomers Methyl methacrylate (MMA) and Butyl Acrylate (BA) were procured from Aldrich, New Delhi. They were used after purification by alkali method. Free radical initiator potassium persulfate (KPS; Thomas Baker, Mumbai) and emulsifier sodium lauryl sulphate (SLS; Thomas Baker) were used as received. Crosslinker polypropylene glycol diacrylate (PPGDA) was prepared in laboratory (Shukla *et al.* 2013) by using polypropylene glycol 400 (PPG400; Thomas Baker) and acrylic acid (AA; Thomas Baker). Deionized water was used throughout the experimental work.

2.2 Polymerization

The emulsion polymerization was carried out in a 500 mL three-necked round-bottom flask, equipped with stirrer, reflux condenser, dropping funnel, and a thermometer. Polymer latex samples were prepared by thermally initiated free radical polymerization (KPS as initiator) of MMA and BA in the presence and absence of crosslinker as monomer PPGDA. The polymerization reaction was carried out at temperature 70+1 °C, using emulsifier SLS for a course of 3 hours. The percentage conversion of synthesized latex is varied with the feed ratio of monomer (Bajpai *et al.* 2009). The selected synthesized latex was coated on clean and smooth substrates as glass. The films were dried for 1 hour in a hot air oven to remove most of the water present as solvent. The thickness of the dried films in case of all the polymer ratio synthesized, namely SA_5, SA_{51}, and SA_{52}, was maintained as 0.1 + 0.05 mm. The actual feed compositions and designations of polymers are given in Table 1.

2.3 Swelling Kinetics of Latex Films

Gravimetric analysis is used to determine the degree of swelling. In every experiment, a pre-weighed cured sample was suspended in a beaker of distilled water at room temperature. The film was taken out from the water at different time intervals, quickly blotted free of surface water by using filter paper, weighed on analytical balance, and returned again to the swelling medium. The swelling ratio and degree of swelling were calculated using equation 1 (Frisch *et al.*1969).

Table 1. Monomer feed compositions (MMA/BA/PPGDA)

Polymer Code	Mole Ratio of Monomers		Weight Percentage of Monomers			Amount of MMA (g)	Amount of BA (g)	Amount of PPGDA (g)
	MMA	BA	MMA	BA	PPGDA			
SA_5	5	5	50	50	0	21.9	28.1	0
SA_{51}	5	5	41.6	53.3	5	20.8	26.6	2.5
SA_{52}	5	5	39.4	50.5	10	19.7	19.7	5

$$\text{Swelling ratio} = \frac{W_s}{W_d} \quad \dots (1),$$

$$\text{Degree of swelling (\%)} \frac{W_s - W_d}{W_d} \times 100$$

where W_d and W_s denote the weight of dry and swollen films, respectively.

3. MATHEMATICAL MODELLING OF SWELLING CONTENT OF POLYMER

This study focuses on mathematical modeling of the swelling behavior of polymers. Several well-established methods have been utilized in this study, which include the application of Peleg's model (2), the first-order absorption kinetic model (3), and the exponential association equation (4) (Vasudeva *et al.* 2010; Noshad *et al.* 2012; Zeinali Kalkhoran *et al.* 2018). Peleg introduced a two-parameter model (equation 2) for characterizing the swelling content of polymers (Vasudeva *et al.* 2010):

$$C = C_0 \pm \frac{t}{k_1 + k_2} \quad \dots (2),$$

where C represents the swelling content at any time t (g/g d.b.), C_0 is the initial swelling measurement at t = 0 (g/g d.b.), k_1 is the kinetic constant of the model (h (g d.b.)/g), k_2 is a characteristic constant of the model (g d.b.)/g).

In equation (2), the sign "±" changes to "+" if the process pertains to absorption or adsorption, and to "–" if it pertains to drying or desorption. The first-order absorption kinetic model employs the following equation (Grnicki *et al.* 2013):

$$C = C_e + (C_0 - C_e)\exp(-k_{r1}t) \quad \dots (3)$$

where, C_e represents the equilibrium swelling content, k_{r1} is the swelling kinetic constant (h^{-1}). The exponential association equation is expressed by equation (4):

$$C = C_e\left[1 - \exp(-k_{r2}t)\right] \quad \dots (4)$$

where, k_{r2} is the kinetic constant (h^{-1}).

These equations help in quantifying and understanding the swelling behavior of polymers under different conditions, like absorption, adsorption, drying, and desorption processes. This study carries significant importance in the field of polymer research for several reasons:

1. **Understanding Polymer Expansion in Various Conditions**: These models provide a useful set of tools for studying polymer expansion in different situations. By using these models, scientists can better grasp how polymers react to processes like soaking up liquids, sticking to surfaces, drying out, and releasing absorbed substances. This flexibility is important because polymers are used in many different ways, and their swelling behavior can change based on the situation.

2. **Parameter Estimation for Comprehensive Polymer Swelling Analysis**: In these models, several parameters come into play, including kinetic constants (k_1, k_2, k_{r1}, and k_{r2}) and initial swelling content (C_0). When researchers match real-world data with these models, they can determine these parameters. This process offers insights into fundamental physical and chemical processes that control polymer swelling. This parameter estimation plays a crucial role in quantitatively characterizing polymer behavior.

3. **Comparative Analysis for Model Selection:** By employing multiple models, researchers can conduct a comparative analysis to determine which model aligns best with their experimental data. This method aids in choosing the most suitable model for a specific polymer or process. This comparative approach improves the precision and trustworthiness of the research outcomes.

4. **Predictive Abilities**: After successfully fitting these models to real-world data, they can be used to make predictions. Researchers can use them to anticipate how polymers will behave in different situations or over time. This valuable information can help in making choices about which materials to use and how to optimize processes.

5. **Scientific Progress:** Above mentioned models help to advance our scientific knowledge in the field of polymer science. Researchers can use these models as a foundation to create more detailed and accurate descriptions of how polymers behave. This deeper understanding of polymer properties and behavior contributes to the overall growth of our knowledge in the field.

Hence, using these models in polymer research allows researchers to thoroughly study and grasp polymer swelling behavior. It empowers them to make predictions and addition to the extensive pool of scientific knowledge in this field. This knowledge proves invaluable in designing materials and processes across diverse industries such as pharmaceuticals, agriculture, and materials science.

4. STATISTICAL ANALYSIS

Statistical analysis of the experimental data was conducted utilizing both MATLAB and Origin Software. The assessment of the fit between the experimental data and all three models was based on several key statistical criteria within a 95% confidence interval. These criteria included Chi-square, Sum of Squared Errors (SSE), R-Square, and Root Mean Square Error (RMSE) (Kaleta *et al.* 2010). The criterion for selecting the best model, favoring the one with the highest R-Square and the least Chi-Square, SSE, and RMSE, is a sound approach. A model with a high R-Square value explains a significant portion of the data's variability, while low values for Chi Square, SSE, and RMSE indicate that the model closely matches the observed data points. This rigorous statistical analysis ensures that the chosen model accurately represents the swelling characteristics of the polymer under investigation, providing confidence in the study's findings and conclusions.

5. EXPERIMENTAL FINDINGS AND DISCUSSION

5.1 Swelling Curves

Swelling plays a crucial role in the characterization of polymers. Fig. 1 illustrates the variations in swelling content over different time intervals. This three-dimensional (3D) chart was generated to represent the combined impact of both time and PPGDA concentration on polymer swelling. This chart serves as a valuable tool for understanding the interplay between these two input variables and their impact on swelling behavior. Notably, it is evident from the absorption curves that the rate of swelling diminishes as the concentration of PPGDA increases. This observation is significant as it indicates that PPGDA concentration plays a pivotal role in modulating the swelling behavior of the polymer. As the concentration rises, the polymer exhibits reduced swelling, suggesting a potential application for controlling and fine-tuning the swelling characteristics of the material. Understanding these relationships between variables is fundamental in tailoring polymer properties for various applications, ranging from drug delivery systems to materials science.

5.2 Evaluation of Peleg Model

Fig. 2 presents the outcomes of the swelling tests conducted at different time intervals for varying PPGDA concentrations, specifically 0%, 5%, and 10%. These experimental results have been fitted to Peleg's

model, which is a powerful tool for characterizing swelling behavior in polymers. The fitted model helps to understand the changes in polymer swelling properties with time and PPGDA concentration.

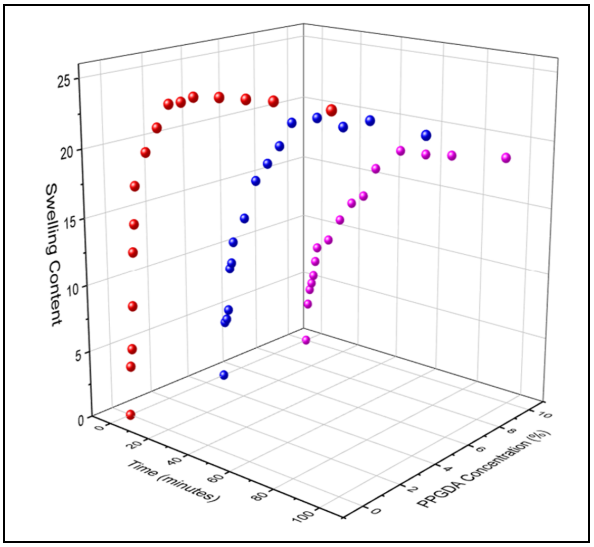


Fig. 1: Swelling content at different PPGDA concentrations 0% (Red), 5% (Blue), 10% (Pink)

The constants k_1 and k_2 for each of the PPGDA concentrations are tested (Table 2). These constants are fundamental to the Peleg model and help quantify the kinetics and characteristics of the swelling process. Additionally, the table includes statistical values associated with the Peleg model, which further validates the model's good fit to the experimental data.

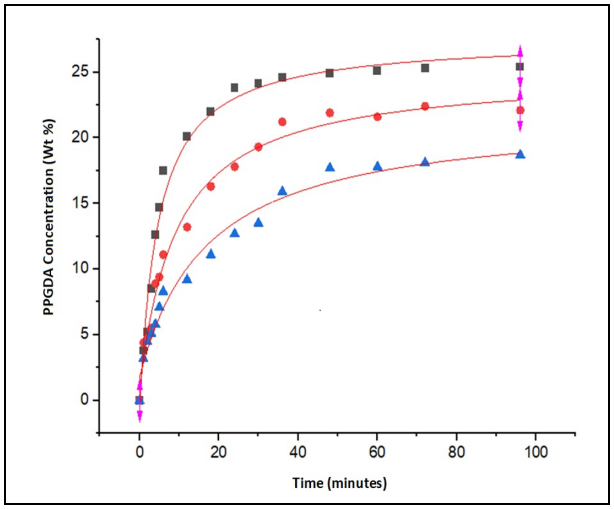


Fig. 2: Peleg model at 0% (Brown), 5% (Red), 10% (Blue) PPGDA concentration

Based on the above information from the Peleg model, various parameters were generated and these values were used to generalize the relationships by formulating expressions for each parameter regarding different PPGDA concentrations. Fig. 3 is a visual representation of how the constants k_1 and k_2 and other model-related parameters vary as a function of PPGDA concentration.

Table 2. Peleg model coefficients and statistical parameters for swelling content at different PPGDA concentrations

PPGDA Concentration (Wt%)	C_0	k_1	k_2	Chi-Square	SSE	R^2	RMSE
0	-1.2293	0.15611	0.03475	1.44548	18.79	0.98121	1.202
5	0.7067	0.37994	0.04116	0.74895	9.736	0.9869	0.8654
10	1.71881	0.83812	0.0497	0.86587	11.26	0.97605	0.9305

In essence, this comprehensive analysis, including experimental data, model fitting, parameter determination, and subsequent generalization contributes significantly to the impact of PPGDA concentration on the swelling characteristics of the polymer. Such insights are invaluable in designing polymers for specific applications in fields such as materials science and pharmaceuticals.

5.3 Evaluation of First-order Absorption Kinetic Model

Fig. 4 displays the experimental results of the swelling tests conducted at various time intervals for different PPGDA concentrations (0%, 5%, and 10%). The data were fitted to the first-order absorption kinetic model, demonstrating how well the model aligns with the actual experimental observations. This fitting process helps assess the model's ability to describe the swelling behavior under different conditions.

Table 3 presents the coefficients associated with the first-order absorption kinetic model for each PPGDA concentration. These coefficients are essential for characterizing the kinetics of the swelling process. The statistical values in the table show the good fit between the model and the experimental data. These statistics help determine the model's reliability and accuracy in representing the swelling behavior.

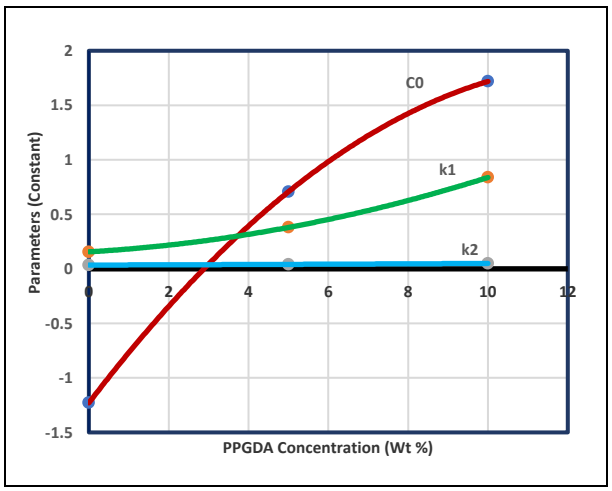


Fig. 3: Impact of PPGDA concentration on various parameters of Peleg Model and their modeling

Overall, this evaluation serves as a critical step in assessing the applicability and performance of the first-order absorption kinetic model in describing polymer swelling under varying PPGDA concentrations. It helps validate the model's effectiveness in capturing the underlying kinetics of the swelling process and provides valuable data for further analysis and application in fields such as materials science and polymer engineering. Based on above information of first-order absorption kinetic model, various parameters were generated and the values were used to generalize the concepts that were formulated for each parameter regarding other PPGDA concentrations (Fig. 5).

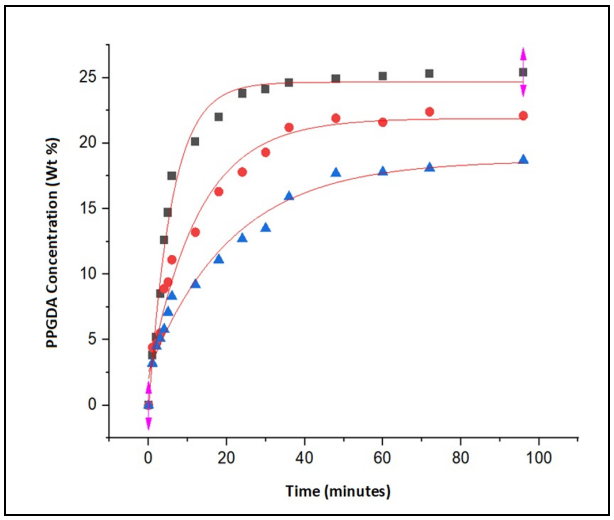


Fig. 4: First-order absorption kinetic model at 0% (Brown), 5% (Red), 10% (Blue) PPGDA concentration

Table 3. First-order absorption kinetic model coefficients and statistical parameters for swelling content at different PPGDA concentrations

PPGDA Concentration (Wt%)	C_0	C_e	k_{r1}	Chi-Square	SSE	R^2	RMSE
0	-0.36407	24.66111	0.16843	1.08042	14.05	0.98596	1.039
5	2.02568	21.89761	0.07864	1.16365	15.13	0.97966	1.079
10	2.55896	18.68602	0.04681	1.15208	14.98	0.96814	1.073

Table 4. Coefficients of the exponential association equation and statistical parameters for swelling content at different PPGDA concentrations

PPGDA Concentration (Wt%)	C_e	k_{r2}	Chi-Square	SSE	R^2	RMSE
0	24.6903	0.16419	1.01841	14.25775	0.9816	1.047
5	21.36377	0.10099	1.73097	24.23355	0.9603	1.365
10	17.44128	0.07438	2.4622	34.47062	0.9124	1.628

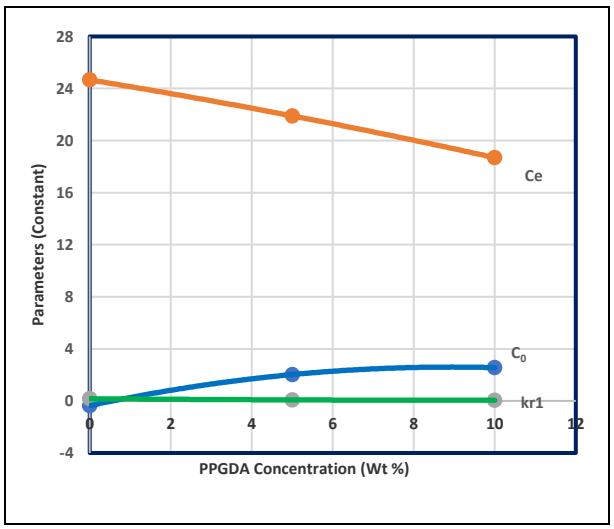


Fig. 5: Impact of PPGDA concentration on various parameters of first-order absorption kinetic model and their modeling

5.4 Evaluation of Exponential Association Equation

Fig. 6 shows the results of swelling test at different times for the various PPGDA concentrations like 0%, 5% and 10% concentration, fitted on exponential association equation.

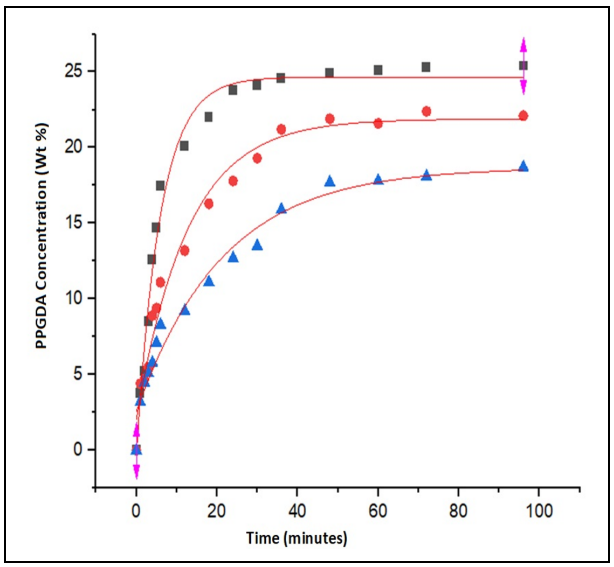


Fig. 6: Exponential association equation at at 0% (Brown), 5% (Red), 10% (Blue) PPGDA concentration

Table 4 shows the coefficients of exponential association equation at various PPGDA concentrations and also represents the statistical values of this model. Based on this information, various parameters were derived and used to generalize the concepts, enabling the formulation of relationships for each parameter across different PPGDA (Fig. 7).

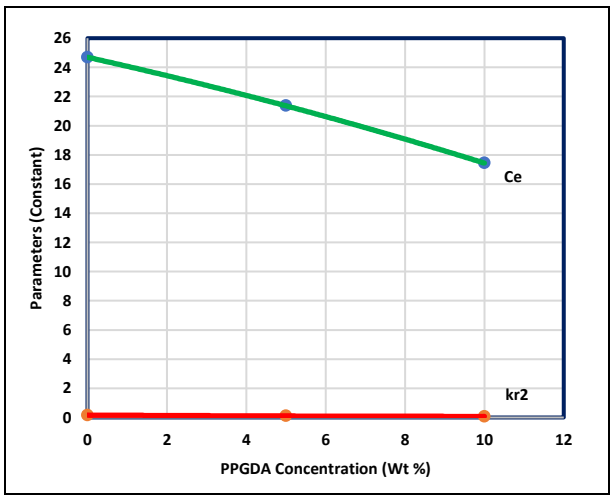


Fig. 7: Impact of PPGDA concentration on various parameters of exponential association equation and their modeling

6. CONCLUSION

The study demonstrates that waterborne polymer latex coatings offer a cost-effective and environmentally safer alternative to solvent-based systems while maintaining high-performance properties. The swelling behavior of the polymer was successfully analyzed using Peleg's model, the first-order absorption model, and the exponential association model, all of which showed good predictive capability. The swelling process exhibited a rapid initial increase followed by a gradual approach to saturation, highlighting its time-dependent nature. Increasing PPGDA concentration influenced the kinetic parameters differently across models, with Peleg constants (k_1 and k_2) increasing, while the first-order (k_{r1}) and exponential (k_{r2}) constants decreased, indicating complex interactions between concentration and swelling dynamics. Among the models, the Peleg model provided the best fit, confirming its suitability for describing polymer swelling under the studied conditions. Overall, the findings provide a clear understanding of the effect of PPGDA concentration on swelling kinetics and support the use of appropriate modeling approaches for optimizing polymer performance in practical applications.

ACKNOWLEDGEMENTS

We would like to thank the Director, KIET Group of Institutions, Ghaziabad for guidance and motivation to carry out this work.

FUNDING

This research received no specific grant from any funding agency in the public, commercial, or not-for-profit sectors.

CONFLICTS OF INTEREST

The authors declare that there is no conflict of interest.

COPYRIGHT

This article is an open-access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (http://creativecommons.org/licenses/by/4.0/).



REFERENCES

Bajpai, S., Rai, J. S. P. and Nigam, I., Swelling behavior of poly(MMA- co -BA- co -PPGDA) polymers, *J. Appl. Polym. Sci.* 112(4), 2374–2382 (2009). https://doi.org/10.1002/app.29717

Frisch, H. L., Wang, T. T. and Kwei, T. K., Diffusion in glassy polymers. II, *J. Polym. Sci. Part A-2 Polym. Phys.,* 7(5), 879–887 (1969). https://doi.org/10.1002/pol.1969.160070512

Grnicki, K., Kaleta, A., Winiczenko, R., Chojnacka, A. and Janaszek, M., Some Remarks on Modelling of Mass Transfer Kinetics During Rehydration of Dried Fruits and Vegetables, In: Mass Transfer - Advances in Sustainable Energy and Environment Oriented Numerical Modeling. *InTech*, (2013). https://doi.org/10.5772/54072

Kaleta, A. and Górnicki, K., Some remarks on evaluation of drying models of red beet particles, *Energy Convers. Manag.,* 51(12), 2967–2978 (2010). https://doi.org/10.1016/j.enconman.2010.06.040

Kane, R. S., Fabricating Complex Polymeric Micro- and Nanostructures: Lithography in Microfluidic Devices, *Angew. Chemie Int. Ed.,* 47(8), 1368–1370 (2008). https://doi.org/10.1002/anie.200704426

Kang, Y., Pitto-Barry, A., Willcock, H., Quan, W.-D., Kirby, N., Sanchez, A. M. and O'Reilly, R. K., Exploiting nucleobase-containing materials – from monomers to complex morphologies using RAFT dispersion polymerization, *Polym. Chem.,* 6(1), 106–117 (2015). https://doi.org/10.1039/C4PY01074D

McKenna, T. F., Graillat, C. and Guillot, J., Contributions to defining the rate constants for the homo- and copolymerisation of butyl acrylate and vinyl acetate, *Polym. Bull.,* 34(3), 361–368 (1995). https://doi.org/10.1007/BF00294156

Noshad, M., Mohebbi, M., Shahidi, F. and Mortazavi, S. A., Kinetic modeling of rehydration in air-dried quinces pretreated with osmotic dehydration and ultrasonic, *J. Food Process. Preserv.,* 36(5), 383–392 (2012). https://doi.org/10.1111/j.1745-4549.2011.00593.x

Pladis, P., Alexopoulos, A. H. and Kiparissides, C., Mathematical Modeling and Simulation of Vinylidene Fluoride Emulsion Polymerization, *Ind. Eng. Chem. Res.,* 53(18), 7352–7364 (2014). https://doi.org/10.1021/ie403548m

Shukla, S. and Rai, J. S. P., Synthesis and kinetic study of diacrylate and dimethacrylate, *Int. J. Plast. Technol.,* 17(2), 182–193 (2013). https://doi.org/10.1007/s12588-013-9058-4

Vasudeva, S., Vishwanathan, K. H., Aswathanarayana, K. N. and Indhudhara Swamy, Y. M., Hydration behaviour of food grains and modelling their moisture pick up as per Peleg's equation: Part I, Cereals, *J. Food Sci. Technol.,* 47(1), 34–41 (2010). https://doi.org/10.1007/s13197-010-0012-6

Zeinali Kalkhoran, A. H., Vahidi, O., Naghib, S. M., A new mathematical approach to predict the actual drug release from hydrogels, *Eur. J. Pharm. Sci.,* 111, 303–310 (2018). https://doi.org/10.1016/j.ejps.2017.09.038

Zhou, C., Xu, S., Pi, P., Cheng, J., Wang, L., Yang, J., Wen, X., Polyacrylate/silica nanoparticles hybrid emulsion coating with high silica content for high hardness and dry-wear-resistant, *Prog. Org. Coatings,* 121, 30–37 (2018). https://doi.org/10.1016/j.porgcoat.2018.04.001

Zhu, S., Tian, Y., Hamielec, A. E., Eaton, D. R., Radical trapping and termination in free-radical polymerization of methyl methacrylate, *Macromol.,* 23(4), 1144–1150 (1990). https://doi.org/10.1021/ma00206a037